



# INTERNATIONAL JOURNAL OF ADVANCE RESEARCH, IDEAS AND INNOVATIONS IN TECHNOLOGY

ISSN: 2454-132X

Impact factor: 4.295

(Volume 4, Issue 3)

Available online at: [www.ijariit.com](http://www.ijariit.com)

## Influence of heat treatment on mechanical properties of aluminum matrix composites

G. Ramesh

[gramesh\\_me@yahoo.co.in](mailto:gramesh_me@yahoo.co.in)

MEA Engineering College,  
Malappuram, Kerala

B. Gopinath

[gopi\\_npaktg@yahoo.co.in](mailto:gopi_npaktg@yahoo.co.in)

NPA Centenary Politechnic College,  
Kotagiri, Tamil Nadu

H. Harikrishnan

[halan\\_hari@yahoo.com](mailto:halan_hari@yahoo.com)

NPA Centenary Politechnic College,  
Kotagiri, Tamil Nadu

V. C. Uvaraja

[c\\_uva@rediffmail.com](mailto:c_uva@rediffmail.com)

Bannari Amman Institute of Technology,  
Coimbatore, Tamil Nadu

Praatyush Rao .N

[pratyushrao04@gmail.com](mailto:pratyushrao04@gmail.com)

Rajalakshmi Engineering College,  
Chennai, Tamil Nadu

### ABSTRACT

*The Al 7075 alloy matrix materials possess mechanical properties with the addition of SiC particulates as reinforcement. Stir casting is used for preparing composite workpiece. Composites were adopted for heat treatment process by subjecting to solutionizing followed by quenching in ice media for improving the mechanical properties. Then the specimens are brought to artificial aging at a temperature of 140°C for different time duration. The hardness properties are examined for the composite materials before and after heat treatment.*

**Keywords:** Aluminum alloy, Artificial aging, Hardness

### 1. INTRODUCTION

In engineering materials system, the heat treatment processes are incredibly essential for improving the composite material properties. The main purpose of the heat treatment is to create the material system structurally and physically strong and fit for engineering application [1]. Heat treatment of aluminium alloys favors the maximum concentration of hardening solute to dissolve into solution. This method is suspiciously conceded out by heat treatment of an alloy to a temperature at which one single, solid phase exists. By this heat treatment, the solute atoms that are originally part of a two-phase solid dissolve into solution and originates as one single phase. Once the alloy is heated to the recommended solutionizing temperature, it is quenched at a rapid rate such that the solute atoms don't have enough time to precipitate out of the solution. As a result of the quench, a supersaturated solution now exists between solute and aluminium matrix [2, 3].

Rapid quenching creates a saturated solution resulting in increased hardness and mechanical properties of the material system. In addition to these studies, the highest degree of corrosion resistance is obtained through maximum rates of quenching [4]. Quenching takes place in three distinct stages namely vapor blanket stage, boiling stage and liquid cooling stage. The vapour blanket stage begins when hot part submerged in an unbroken blanket which surrounds the object. This blanket exists between the specimen and quenching media if the heat from the surface of the object exceeds the amount of heat needed to form maximum vapour per unit area of the object.

Previous studies [5-14] of the ageing behavior of the composite with discontinuous ceramic reinforcement are different from that of the aluminium matrix alloys.

### Materials Selection

In this paper, SiC particulates reinforced with Al 7075 matrix composite is selected. The nominal chemical composition of Al 7075 alloy are given in Table 1. The hardness of the specimens was measured using Brinell microhardness tester by applying a load of 100 kgf and the average hardness from 10 different data of the experiments was considered.

**Table 1: Chemical composition of Al7075 by weight percentage**

Elements	Si	Fe	Cu	Mn	Ni	Zn	Ti	Mg	Cr	Al
% wt	0.06	0.18	1.62	0.074	0.05	5.62	0.049	2.52	0.22	Balance

### Preparation of Hybrid Aluminum Metal Matrix Composites (HAMMCs)

Stir casting technique is used to fabricate Al 7075 alloys with a varying weight percentage of SiC reinforcement. The stirrer is used to stir the molten metal in semisolid state. The melt was maintained at a temperature of 800°C for one hour. Vortex was created by using a mechanical stirrer. One specimen Al7075 reinforced with 3% SiC, were made with the same procedure. Hardness measurements were carried out on the specimen. Specimen were tested using Rockwell hardness tester machine. A load of 100 Kgf for a period of 15 seconds was applied with a ball indenter of 10 mm diameter. The test was carried out in five different regions. Hardness was determined by measuring the indentations diameter produced. The average of all the five readings was taken as the hardness of the composite.


### Heat Treatment Process

Al 7075 matrix alloy with SiC particulates reinforced composites were subjected to solutionizing treatment at a temperature of 475°C for a period of 2 hr. using muffle furnace, followed by quenching in three different quenchants viz, air, water. Artificial ageing treatment was carried out for the duration of 2 hr. to 10 hr. in steps of 2 hr.


## 2. RESULTS AND DISCUSSION

### Hardness Survey:

Hardness test was carried out using Rockwell hardness tester and then the average values were used to calculate hardness number. A considerable increase in hardness of the matrix was seen with the addition of SiC particles. It is observed that with increased weight % of reinforcement in the matrix alloy, there is a significant improvement in the hardness of the composites. The hardness of HAMMCs increases with a weight percentage of particulate in the Al alloy matrix.

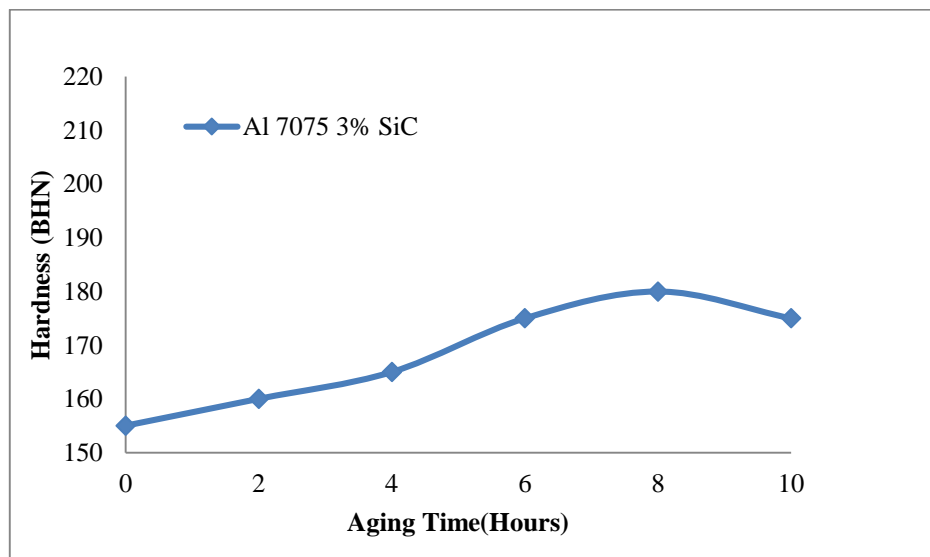

**Fig. 1: Solutionizing Temperature: 475°C, Quenching Media: Ice, Ageing Temp: 140°C**

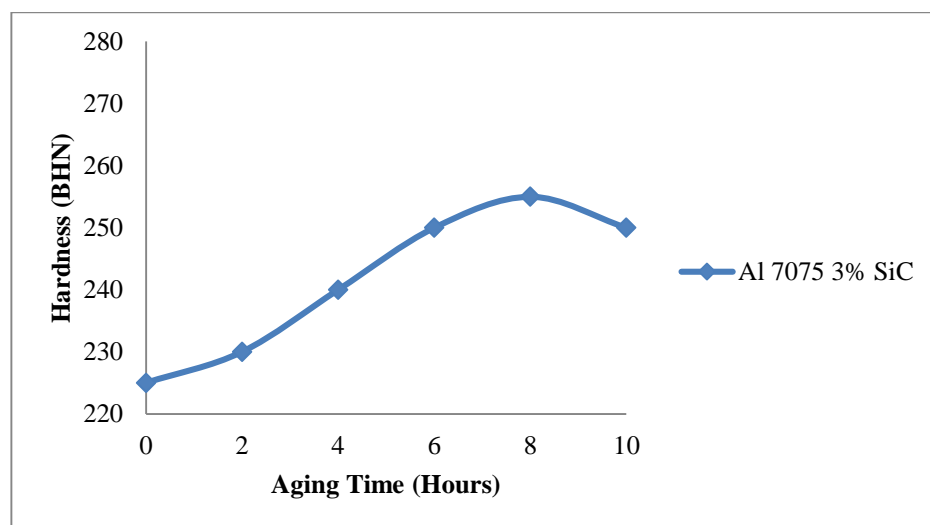

**Fig. 2: Solutionizing Temperature: 475°C, Quenching Media: Ice, Ageing Temp: 140°C**

## 3. CONCLUSION

Hardness increases with ageing duration reach a peak value at 8 hr. and with further increase in ageing duration, there is a decrease in hardness. The hardness of composites increased with increased content of SiC. Heat treatment has a significant effect on the hardness of Al 7075 matrix composites.

#### **4. REFERENCES**

- [1] Rajan TV, Sharma CP, Ashok Sharma. Heat treatment principles Techniques, Rajkamal Electric Press, India, 1998, 142-149.
- [2] Davis JR. Aluminium and aluminium alloys, in ASM especially Handbook, ASM International, Metal Parts, Ohio, 1993.
- [3] Callister WD. Journal-Material Science & Engineering, 1997, 511-531.
- [4] Rollanson EC. Metallurgy for engineers, Edward Arnold Ltd, London, 1998.
- [5] Ribes H, Surey M. Sci metal., 1989, 23,705-709,
- [6] Janowski GM, Pletka BJ. Metal Mater, 1995, A 26, 3027-3034.
- [7] Appendino P, Badini C. Mater. Sci & Eng. 1991, A 135, 275-279.
- [8] El-Baradie, ZM, El-Shah at OA, Abd El-Ajim AN. J.Mater. Process. Tech., 1998, 1-8.
- [9] Amigo V, Ortiz JL, Salvador MO, Serim. 2000, 12, 12383-388.
- [10] Sulvo L, Esperance GL, Surey M, legoux JG. Mater.Sci.Eng., 1994, A 177, 173-183.
- [11] Lewandowski J, Liu C, Hunt WH, Jr. "Effects of Microstructure and Particle Clustering on Fracture of an Aluminum Metal Matrix Composite," Mater. Sci. Eng. 1989, A107, 241-255.
- [12] Kreider KG. "Composite Materials, Metallic Matrix Composites," Academic Press, New York, 1974, 4.
- [13] Rozak G, Lewandowski J J, Wallace J F, Altmisoglu A. "Effects of Casting Conditions and Deformation Processing on A356 Aluminum and A356-20 % SiC Composites," J. Compos. Mater, 1992, 26(14), 2076-2106.
- [14] Prasad BK, "Investigation into sliding wear performance of zinc-based alloy reinforced with SiC particles in dry and lubricated conditions", Wear, 2007, 262, 3-4,262-273.